

AD-R183 114

OPTICAL AND ESR STUDIES OF CO(2+): BETA' ALUMINA(U)
CALIFORNIA UNIV LOS ANGELES DEPT OF MATERIALS SCIENCE
AND ENGINEERING B DUNN ET AL. 01 JUL 87 TR-10

1/1


UNCLASSIFIED

N00014-83-K-0498

F/G 7/2

NL



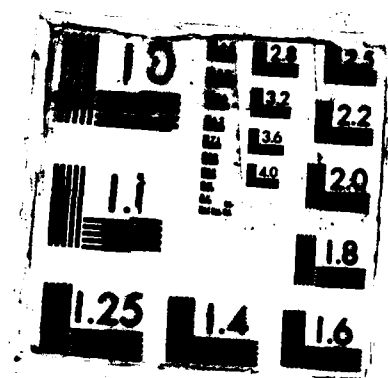

DTIC FILE COPY

AD-A183 114

12

OFFICE OF NAVAL RESEARCH

Contract N00014-83-K-0498

R&T Code 413d011--02

Technical Report No. 10

Optical and ESR Studies of Co^{2+} : Beta" Alumina

by

B. Dunn¹, J.D. Barrie¹ and D. Vivien²

Prepared for Publication

in the

Journal of Materials Science Letters

1. Department of Materials Science and Engineering,
University of California, Los Angeles,
Los Angeles, California 90024

2. Universite Pierre et Marie Curie, ENSCP
Paris, France

July 1, 1987

DTIC
ELECTE
JUL 27 1987
S D
GE

Reproduction in whole or in part is permitted for
any purpose of the United States Government.

This document has been approved for public release and sale;
its distribution is unlimited.

27 2 2 100

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION/AVAILABILITY OF REPORT Approved for public release and sale; its distribution is unlimited	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) Technical Report No. 10		5. MONITORING ORGANIZATION REPORT NUMBER(S)	
6a. NAME OF PERFORMING ORGANIZATION Dept. of Materials Science and Engineering	6b. OFFICE SYMBOL (if applicable)	7a. NAME OF MONITORING ORGANIZATION Office of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) 6531 Boelter Hall University of California, Los Angeles Los Angeles, CA 90024		7b. ADDRESS (City, State, and ZIP Code) 800 N. Quincy Street Arlington, VA 22217	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Same as #7 above	8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-83-K-0498	
8c. ADDRESS (City, State, and ZIP Code)		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO.	PROJECT NO.
		TASK NO.	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) Optical and ESR Studies of Co^{2+} : Beta" Alumina			
12. PERSONAL AUTHOR(S) B. Dunn, J. D. Barrie and D. Vivien			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM 9/86 TO 8/87	14. DATE OF REPORT (Year, Month, Day) 1987, July 1	15. PAGE COUNT
16. SUPPLEMENTARY NOTATION Submitted to Journal of Materials Science letters			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	
19. ABSTRACT (Continue on reverse if necessary and identify by block number) Optical absorption and ESR spectroscopy were used to identify the site symmetry for Co^{2+} in beta" alumina. Optical absorption indicated occupancy of a tetrahedral site with $D_q = 410 \text{ cm}^{-1}$ and $B = 800 \text{ cm}^{-1}$. There was no evidence of Co^{2+} in octahedral symmetry. ESR spectra indicated Co^{2+} in an axial symmetric site to the C-axis. This is likely to be the Beevers-Ross site which has C_{3v} symmetry. The parameters $g = 2.16$ and $g = 4.59$ are consistent with this assignment.			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL		22b. TELEPHONE (Include Area Code)	22c. OFFICE SYMBOL

OPTICAL AND ESR STUDIES OF $\text{Co}^{2+}:\beta$ ALUMINA

B. Dunn and J. D. Barrie
Department of Materials Science and Engineering
University of California, Los Angeles

D. Vivien
Laboratoire de Chimie
Appliquee de l'Etat Solide
Universite Pierre et Marie Curie
ENSCP
Paris, France

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input checked="" type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

β alumina
 The β aluminas have recently been reported to exhibit several interesting optical properties, including lasing action. (1) The materials are doped by ion exchange reactions, and techniques for introducing numerous lanthanide and transition metal ions have been demonstrated. (2, 3) Among the transition metal ions, Co^{2+} is of interest for tunable laser systems in the infra red because of the ${}^4T_2 \rightarrow {}^4T_1(F)$ transition which occurs in an octahedral crystal field. (4) As a laser host for Co^{2+} β alumina is potentially significant because previous crystallographic studies of Mn^{2+} and Zn^{2+} β aluminas indicated that the transition metal ions occupied both octahedral and tetrahedral sites within the conduction plane. (5) In the present paper we use optical absorption and ESR spectra to help identify the site symmetry for Co^{2+} in β alumina.

Co^{2+} was introduced in the β'' alumina structure by ion exchange reactions. [3] In this approach, single crystals of Na β'' alumina (nominally, $\text{Na}_{1.67}\text{Mg}_{0.67}\text{Al}_{10.33}\text{O}_{17}$) were immersed in CoCl_2 or in eutectic NaCl-CoCl_2 melts at 700 and 750 ° C. The composition of the resulting crystals was $\text{Na}_{1.67-2x}\text{Co}_x\text{Mg}_{0.67}\text{Al}_{10.33}\text{O}_{17}$ (where x varied from 0.67 to 0.80) and they were colored a deep blue. The use of ion exchange reactions at these relatively low temperatures ensured that the exchanged ion (i.e., Co^{2+}) could not diffuse into the spinel blocks and thus resided within the conduction plane. There are two types of sites available for the ion; the mid-oxygen (octahedral) and the Beevers-Ross and anti-Beevers-Ross sites (both tetrahedral). It is interesting to note that when Co^{2+} was added in high temperature crystal growth studies involving β alumina [6] or β'' alumina, [7] Co^{2+} occupied tetrahedral sites within the spinel block.

Optical absorption spectra were taken at room temperature over the range of 300 nm to 2500 nm using a Beckman UV 5270 spectrometer. Broad absorption bands with peak values at 580 nm and 1550 nm were observed. The former bands are in good agreement with those reported by Akridge and Kennedy. [8] Although more detailed low temperature spectra were not taken, we were still able to use these bands to estimate values for the crystal field parameters Dq and B using standard procedures. [9] In this case it was assumed, according to the blue color of the crystals, that the Co^{2+} was in a tetrahedral site and that the 583 nm and 1407 nm bands corresponded to the ${}^4A_2 \rightarrow {}^4T_1({}^4P)$ and ${}^4A_2 \rightarrow {}^4T_1({}^4F)$ transitions, respectively. The resulting values of $Dq = 410 \text{ cm}^{-1}$ and $B = 800 \text{ cm}^{-1}$ ($Dq/B = 0.51$) are in reasonable agreement with literature values for Co^{2+} in tetrahedral sites in other host structures. [10, 11] The agreement between the calculated and observed absorption bands are given in Table

1. The transition beyond 2400 nm could not be definitively identified in the present work. The lowering of symmetry, which is C_{3v} rather than T_d , and spin-orbit coupling would account for the splitting and shoulders observed experimentally. Finally, it is important to note that there was no evidence of absorption in the 725-750 nm range which is characteristic of Co^{2+} in octahedral symmetry. [12]

The ESR spectra were recorded on a Bruker ESR 220 D spectrometer operating at X band. Temperatures of approximately 20 K were required because of the short spin-lattice relaxation time for Co^{2+} . The ESR spectrum, taken when the magnetic field, B_0 , was parallel to the c- crystal direction, consisted of a broad single line of linewidth 35 mT. In these Co^{2+} doped β'' alumina samples, we did not observe any distinct lines associated with hyperfine interaction (^{59}Co , $I = 7/2$, 100% abundance) at this or any other orientation. When B_0 rotated in a plane perpendicular to the c- axis, the spectra exhibited no angular variation. In this case there was a single line centered at 140 mT of linewidth 25 mT. The magnitude of this linewidth prevented us from directly observing hyperfine interaction. The angular variation for the ESR line when B_0 was turned in a plane containing the c- axis is shown in Fig. 1. The c- axis occurs at the intensity maximum of the ESR line.

The ESR results indicate that the Co^{2+} ions reside in a single site which is axially symmetric to the c- axis. The one type of site in the β'' alumina conduction plane consistent with this description is the Beevers-Ross (or anti Beevers-Ross) site, which is characterized by C_{3v} symmetry. In addition, the values $g_{||} = 2.16$ and $g_{\perp} = 4.59$ are comparable to the g-tensor components reported for other hosts in which the Co^{2+} were located in sites of C_{3v} symmetry. [10, 13] One other interesting feature to note is that the magnitude of the ESR

linewidth suggests that either substantial disorder exists in the crystal field along directions both perpendicular and parallel to the c-axis, or that there is substantial dipolar interaction between neighboring Co^{2+} ions which are expected to lie within 0.5 nm. [5]

The results of the optical absorption measurements are in good agreement with those of ESR. Both spectra are dominated by Co^{2+} residing in the tetrahedral site in the β'' alumina conduction plane. This behavior is somewhat different from that observed for other ion exchanged transition metal β'' aluminas, [5] however, it is possible that the presence of some octahedral Co^{2+} could be masked by the relatively weak oscillator strength of the Co^{2+} ion in that symmetry and the broad linewidth of the ESR spectra. Finally, it is significant to note that although Co^{2+} in β'' alumina does not appear to be a potential laser system because of its strong preference for tetrahedral sites, other divalent transition-metal ions, such as Ni^{2+} or V^{2+} may prefer octahedral symmetry in β'' alumina and thus be suitable activators for solid state tunable lasers. [4]

ACKNOWLEDGEMENTS

The research was supported in part by the U.S. Office of Naval Research and the Franco-American Commission for Educational Exchange. The experimental assistance of D. Simons and B. Schwarz is appreciated.

References


1. M. Jansen, A. J. Alfrey, O. M. Stafsudd, D. L. Yang, B. Dunn and G. C. Farrington, *Opt. Letts.* 9 (1984) 119.
2. G. C. Farrington, B. Dunn and J. O. Thomas, *Appl. Phys. A.* 32 (1983) 159.
3. J. D. Barrie, B. Dunn, O. M. Stafsudd and G. C. Farrington, *Solid State Ionics* 18/19 (1986) 677.
4. See for example; "Tunable Solid State Lasers," P. Hammerling, A. B. Budgor, A. Pinto eds. *Springer series in Optical Sciences*, Vol. 47 (Springer-Verlag, New York 1985).
5. W. Carillo-Cabrera, J. O. Thomas and G. C. Farrington *Solid State Ionics* 17 (1985) 223.
6. P. D. Denier and J. P. Remeika, *J. Solid State Chem.* 17 (1976) 245.
7. S. Chen, D. R. White, H. Sato, C. J. Sandburg and H. R. Harrison, *Proc. Conf. High Temp. Solid Oxide Electrolytes*, Brookhaven, August 1983, edited by F. J. Salzano, (Brookhaven National Lab., Brookhaven, 1983) Vol. 2, p. 121.
8. J. R. Akridge and J. H. Kennedy, *J. Solid State Chem.* 29 (1979) 68.
9. A. B. P. Lever, "Inorganic Electronic Spectroscopy", (Elsevier, Amsterdam 1984).
10. F. Laville, *Doctoral Thesis Universite Pierre et Marie Curie* (1985).
11. J. Ferguson, D. L. Wood and L. G. Van Uitert, *J. Chem. Phys.* 51 (1969) 2904.
12. R. Borromei, G. Ingleto, L. Oleari and P. Day, *J. Chem. Soc. Faraday Trans. 2* 78 (1982) 1705.
13. L. Banci, A. Bencini, C. Benelli, D. Gatteschi, *Nouv. J. de Chimie* 4 (1980) 593.

Table 1: Observed and calculated results for optical absorption.
Calculated baricenter used $B = 800 \text{ cm}^{-1}$ and $D_q = 410 \text{ cm}^{-1}$

Observed Bands (nm)	Experimental Baricenter (nm)	Calculated Baricenter (nm) $B = 800 \text{ cm}^{-1}$ $D_q = 410 \text{ cm}^{-1}$
550, 580, 620	583	582
1290, 1380, 1550	1407	1407
		2439

Caption

Fig. 1 Angular variation of ESR line for B_0 turning in a plane containing the c-axis.

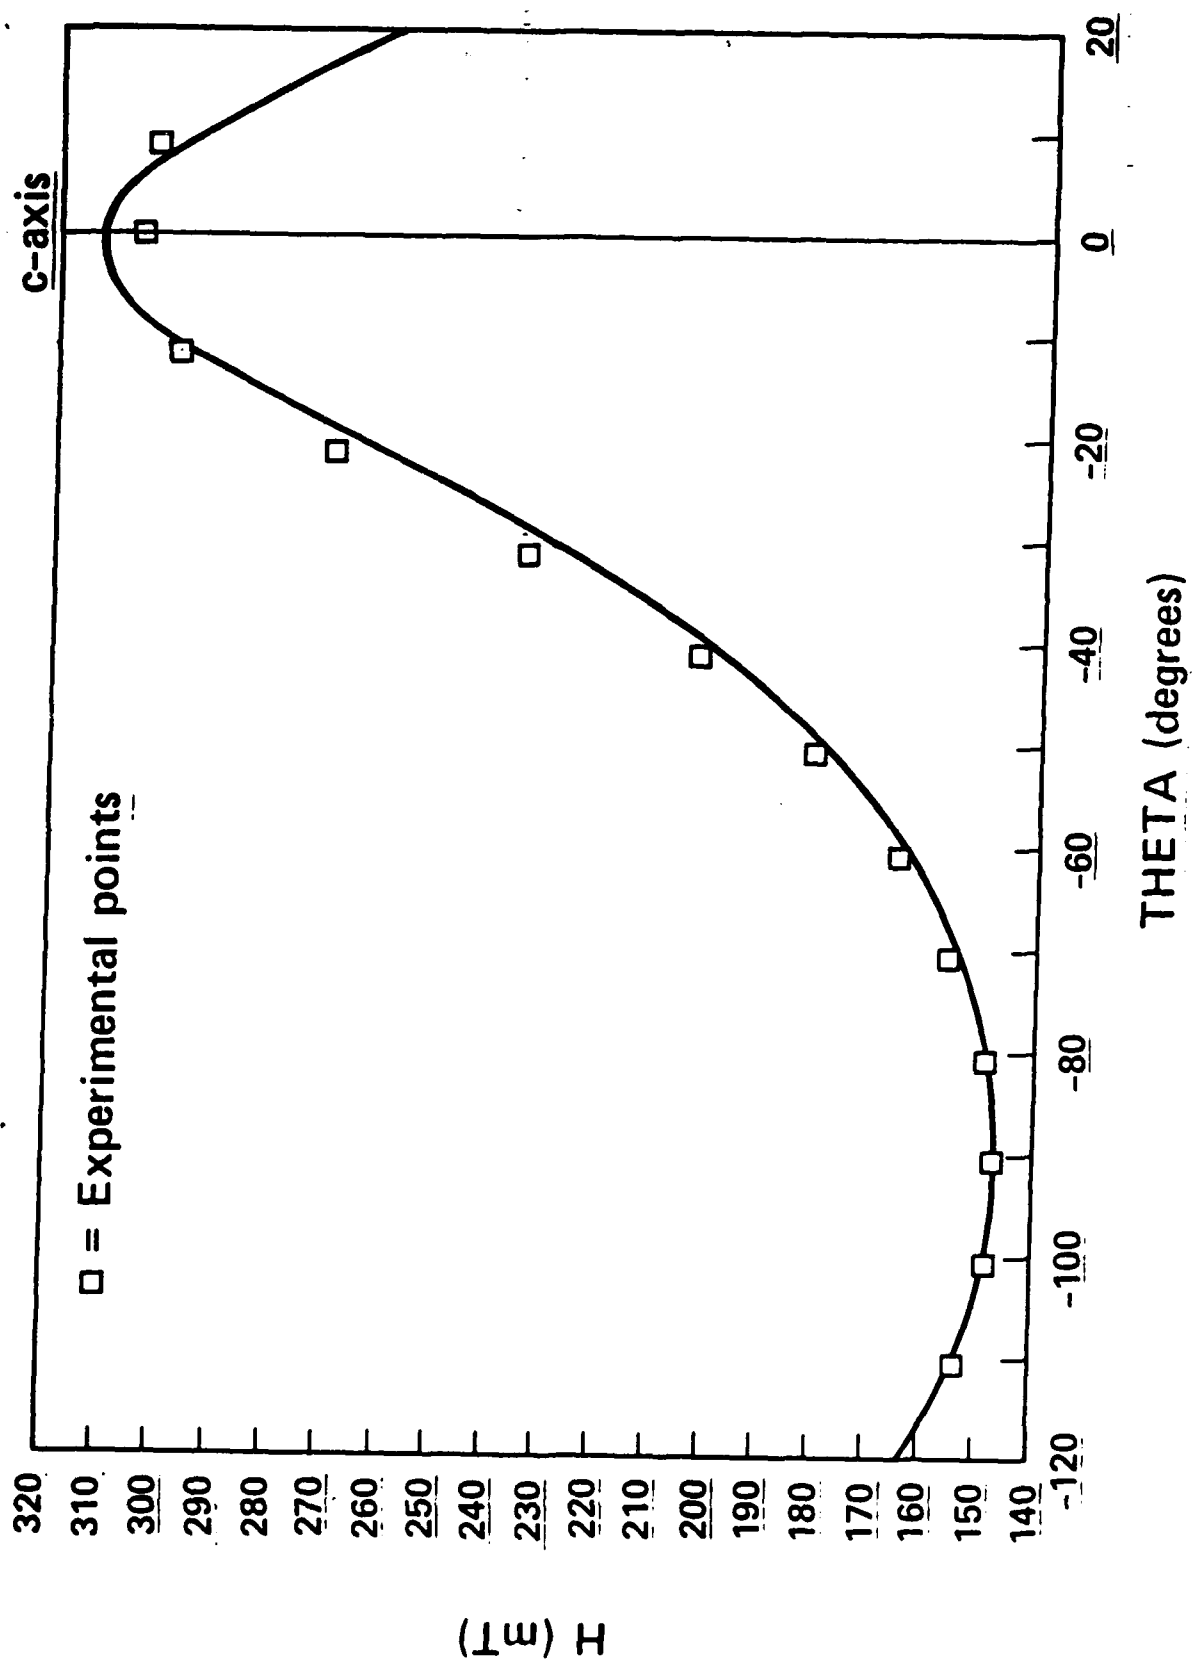

END

9-87

Dtic